

# VITRON IG-6

- Discover the Original



Our glass IG-6 features excellent transmittance and low thermal change in refractive index and dispersion.

IG-6 is ideal for applications in combination with other IR material for color corrected designs and infrared optical systems without thermal defocusing in the 1-12 μm spectrum.

Molding, classical polishing or Single-Point-Diamond-Machining permits the production of optical components with flat, spherical and/or aspherical shaped surfaces for the Infrared and Optoelectronics industries.

Antireflection coatings further improve transmission by reducing the reflection at the air-glass interfaces.

VITRON currently produces 6 different types of Chalcogenide Glasses that are applicable to optics and optoelectronics system design.




Typical delivery in form of blanks:

- ∅ 5 – 150 mm
- 5 – 100 mm
- ct 0.8 – 150 mm

## Index of Refraction (@ 20°C)

λ [μm]	n(λ)
1.00	2.9314
1.50	2.8462
2.00	2.8200
3.00	2.8017
4.00	2.7948
5.00	2.7910
6.00	2.7882
7.00	2.7857
8.00	2.7833
9.00	2.7808
10.00	2.7781
11.00	2.7753
12.00	2.7721

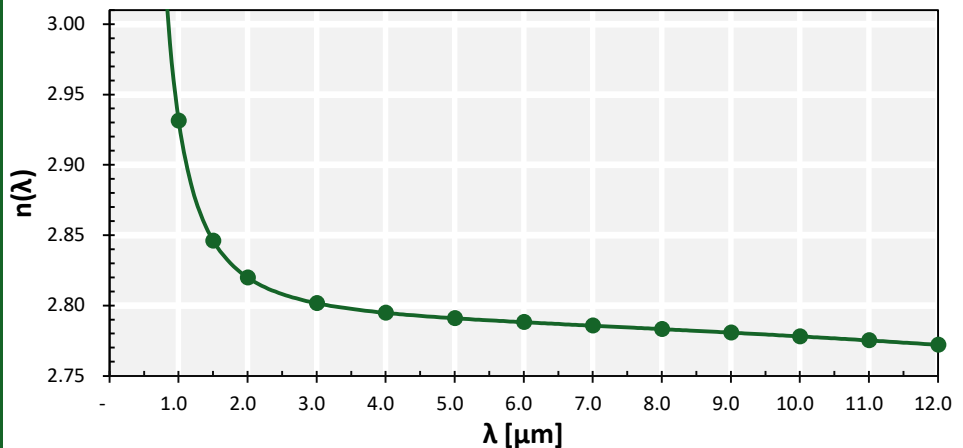

## Sellmeier-Formula (@ 20°C)

A	4.0088
B <sub>1</sub>	3.7706
C <sub>1</sub>	0.4214
B <sub>2</sub>	2.5060
C <sub>2</sub>	61.4227

$$n^2(\lambda; 20) = A + \frac{B_1 \lambda^2}{\lambda^2 - C_1^2} + \frac{B_2 \lambda^2}{\lambda^2 - C_2^2}$$

## Thermo-Optical Coefficient (@ 20°C)

λ <sub>TK</sub>	3.73·10 <sup>-1</sup>
D <sub>0</sub>	2.64·10 <sup>-5</sup>
E <sub>0</sub>	2.72·10 <sup>-5</sup>

$$\frac{dn(\lambda)_{abs}}{dT} = \frac{n^2(\lambda; 20) - 1}{2n(\lambda; 20)} \cdot \left[ D_0 + \frac{E_0}{\lambda^2 - \lambda_{TK}^2} \right]$$

λ [μm]	dn/dT [K <sup>-1</sup> ]
3.4	35.2·10 <sup>-6</sup>
7.0	32.7·10 <sup>-6</sup>
10.6	32.2·10 <sup>-6</sup>

## Dispersion (@ 20°C)

λ [μm]	v <sub>λ</sub>
4.00	168
10.00	159


$$v_4 = \frac{n_4 - 1}{n_3 - n_5}$$

$$v_{10} = \frac{n_{10} - 1}{n_8 - n_{12}}$$

# VITRON IG-6 – Discover the Original

## Transmission

$\lambda$ [ $\mu\text{m}$ ]	$T(\lambda)$ [%]
1.00	53.2
1.50	59.5
2.00	61.2
3.00	60.3
4.00	61.4
5.00	61.9
6.00	62.2
7.00	62.9
8.00	63.5
9.00	62.7
10.00	63.4
11.00	62.8
12.00	61.9
13.00	49.1
14.00	31.5

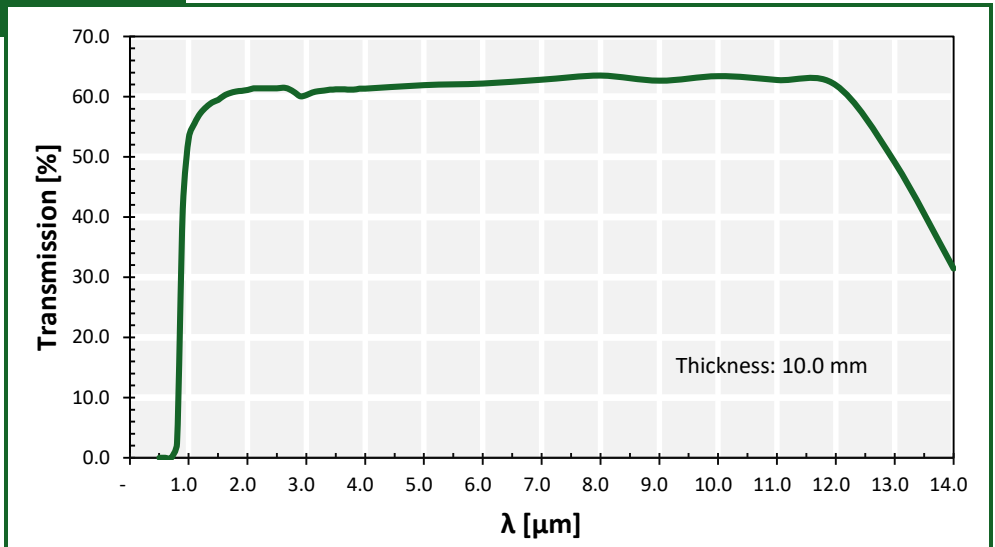

## Material Properties

	As <sub>40</sub> Se <sub>60</sub>	
Composition		
Density	4.63	$\text{g}\cdot\text{cm}^{-3}$
Thermal Expansion (20°C – 100°C)	20.7	$\times 10^{-6} \text{K}^{-1}$
Specific Heat Capacity	0.36	$\text{J}\cdot\text{g}^{-1}\cdot\text{K}^{-1}$
Thermal Conductivity	0.24	$\text{W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$
Transition Temperature	185	°C
Softening Point	236	°C
Young's Modulus	18.3	GPa
Modulus of Rupture	17	MPa
Shear Modulus	8	GPa
Hardness (Knoop)	1.04	GPa

## Chemical Properties

VITRON chalcogenide glasses are insoluble in water. Under normal circumstances, no reactions are observed between glass and organic solvents.

## Typical Forms of Supply

Our chalcogenid glasses are fine-annealed with 3.75 K/h. Variability of the index of refraction: between batches  $\leq 10^{-3}$   
within a batch  $\leq 10^{-4}$

Semi-finished: Boules, Blanks in disk and rectangular shapes, Rods  
Other shapes by customer request

Optical components: Windows, Lenses, Prisms and other optical parts according to customer specification  
AR/AR coatings on customer request

**VITRON**  
Spezialwerkstoffe GmbH  
Maua  
Am Naßtal 5  
D-07751 Jena

Phone: +49-(0)3641-2 88 1-30  
Fax: +49-(0)3641-2 88 1-55  
Email: kontakt@vitron.de  
Internet: www.vitron.de

**VITRON**  
Your Material Specialist